

# On the radiation resistance and thermal durability of silver-exchanged zeolites for trapping radioxenon



Christophe Gueibe<sup>1,2</sup>, Jos Rutten<sup>1</sup>, Johan Camps<sup>1,2</sup>, Dominique Moyaux<sup>3</sup>, Wouter Schroeyers<sup>2</sup>, Grazyna Gryglewicz<sup>4</sup>, Elien Derveaux<sup>2</sup> and Sonja Schreurs<sup>2</sup>

<sup>1</sup> Belgian Nuclear Research Centre (SCK CEN)



<sup>2</sup> Hasselt University (UHasselT), CMK

<sup>3</sup> Institute for RadioElements (IRE)

<sup>4</sup> Wrocław University of Science and Technology

**WOSMIP 2023 - 5 December 2023**


# Content

- Introduction
- Thermal durability 
- Radiation resistance 
- Conclusions & perspectives




# Introduction

- Radioxenon is a key component for the verification of the CTBT
- Detection capability of the IMS noble gas component depends on
  - Number and distribution of stations (31/40)
  - Minimum Detectable Concentration ( $< 1 \text{ mBq/m}^3$  for Xe-133)
  - **Background level from civilian sources at individual stations**

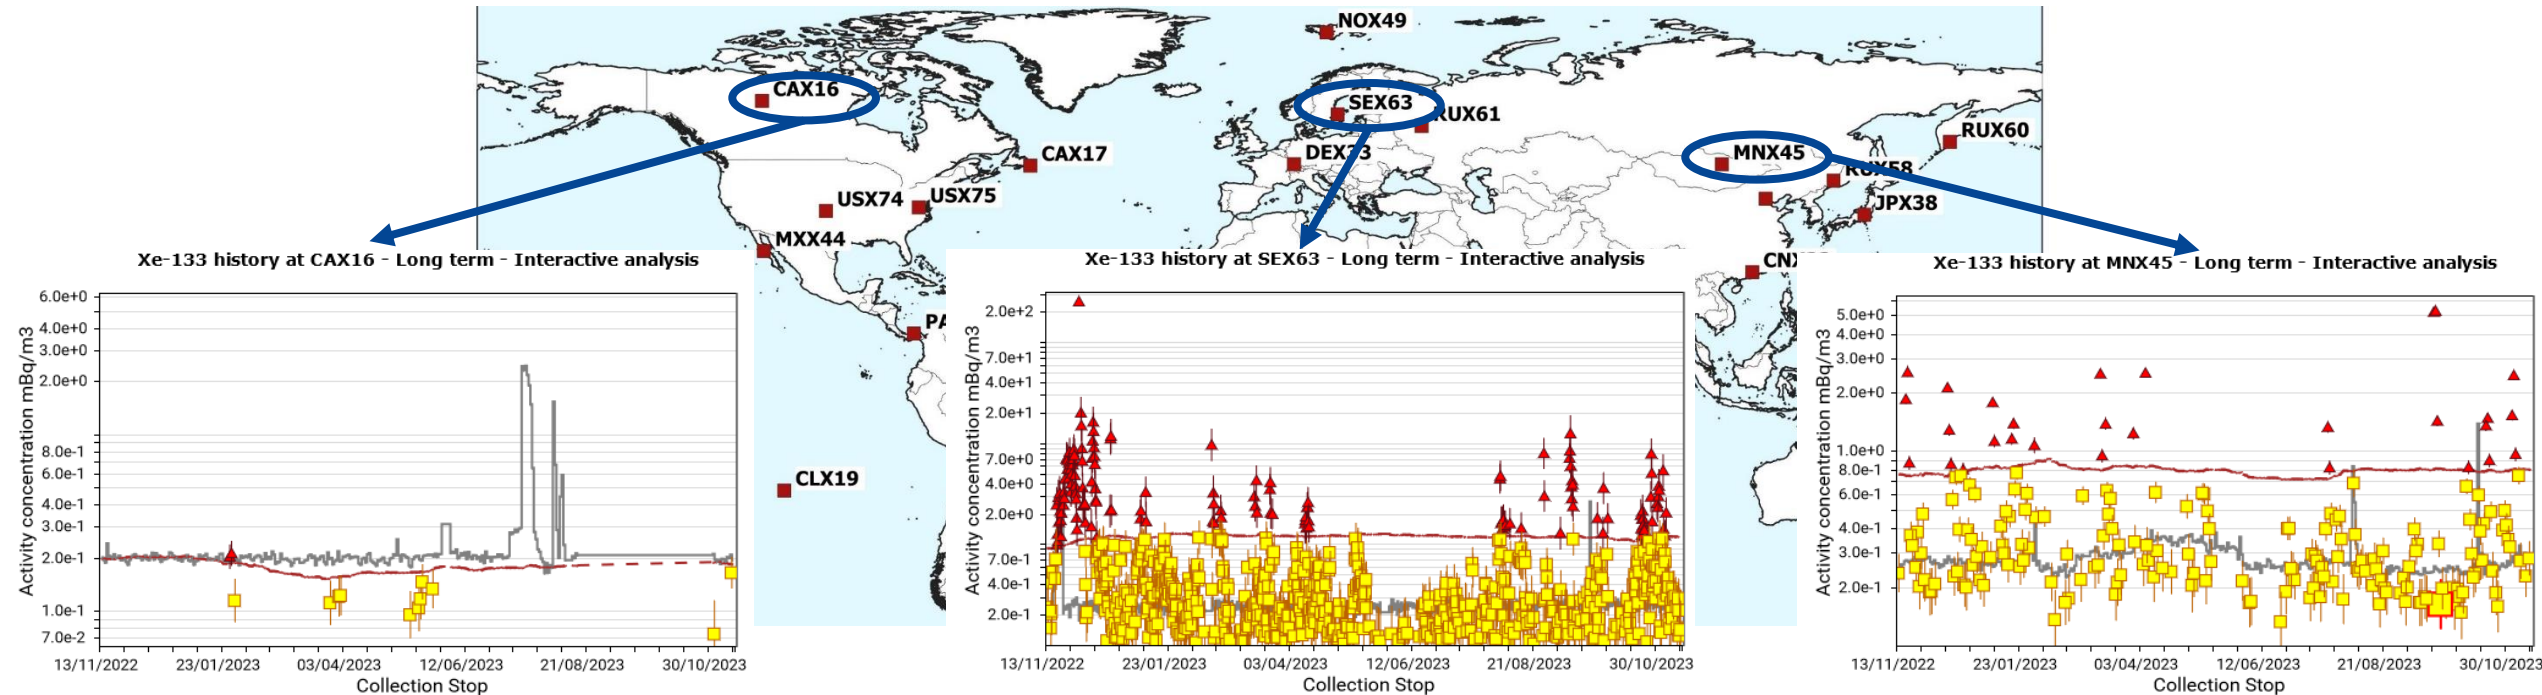

# Minimizing the impact of civilian sources


- Further improve IMS stations to maximize the screening capabilities for the four CTBT-relevant isotopes
- Better understand the sources contributing to the civilian background
- Use of stack monitoring for predicting the civilian background by Atmospheric Transport Modelling
- Further reduce radioxenon emissions from civilian sources (specifically to minimize the impact on the CTBT)

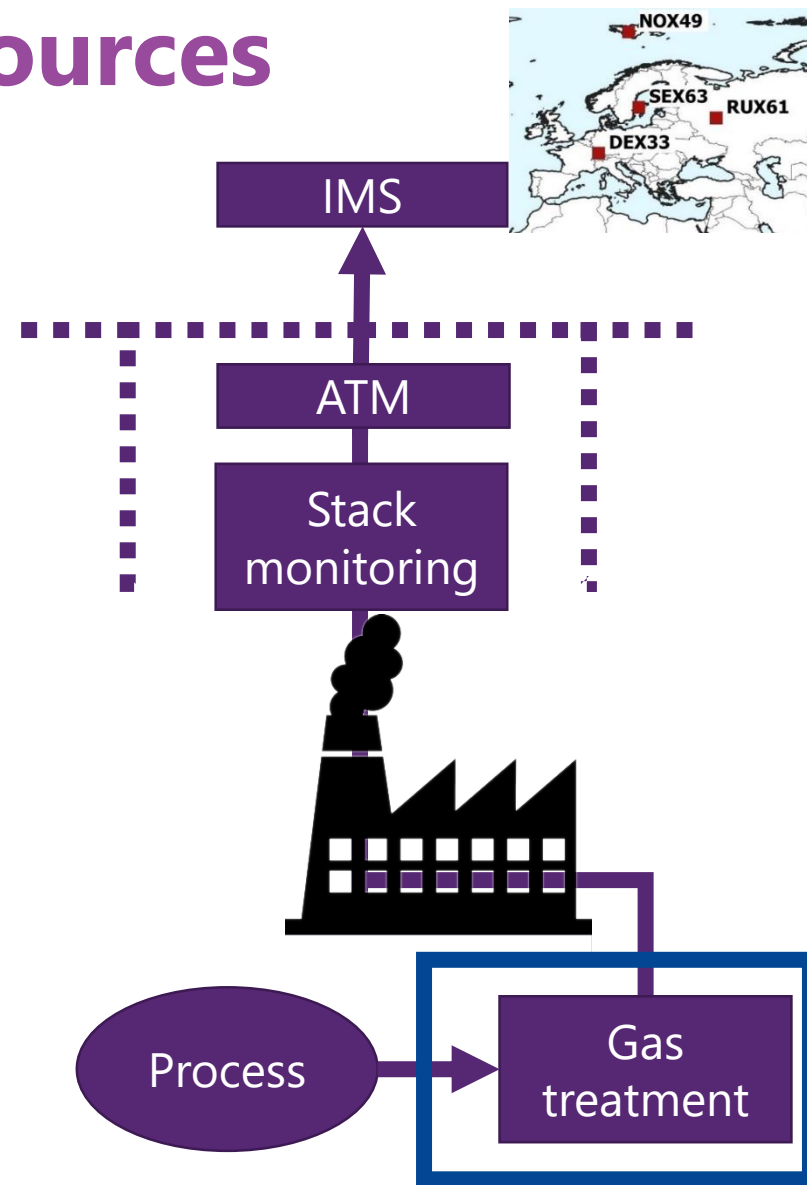


# Further reduce radioxenon emissions ?

- Silver-exchanged zeolites (AgZs) are more efficient than activated carbon
- Room temperature
- $P_{Xe} < 1000 \text{ Pa}$
- Xe in He
  - And in  $N_2$  (also Ar)


**But AgZs are more sensitive to moisture  
 → Moisture traps are needed**

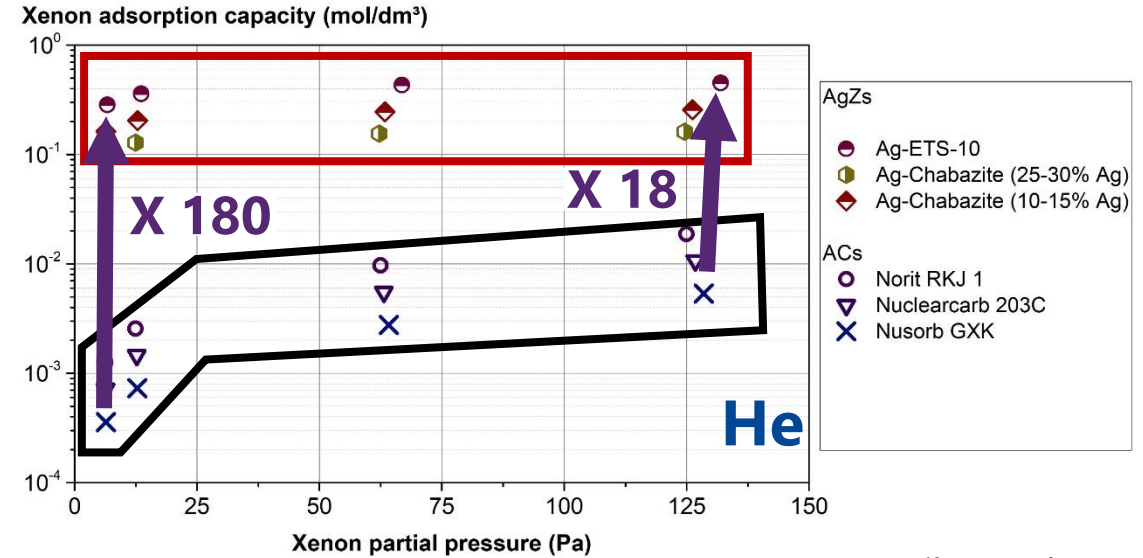

Gueibe et al., 2022  
 Gueibe et al., 2023

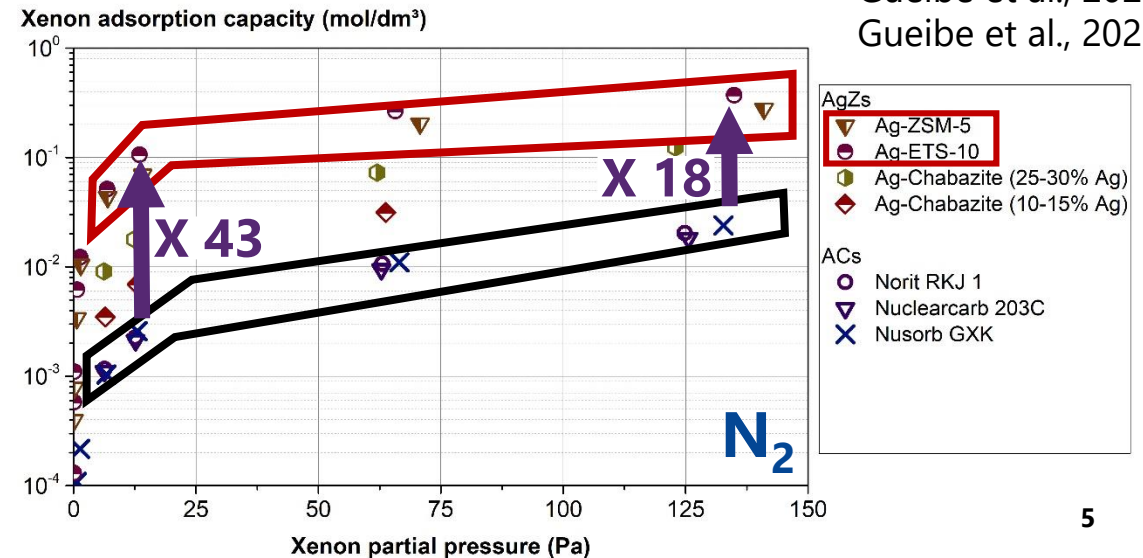

# What is their radiation resistance and thermal regeneration durability ?

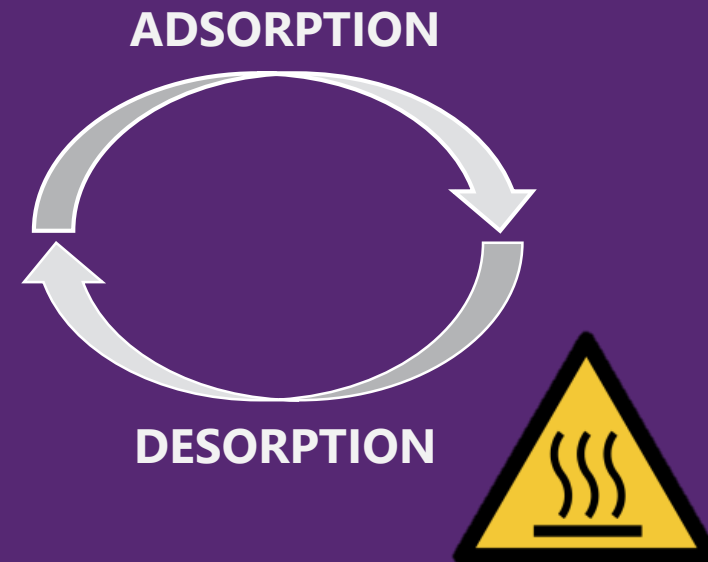


# First exploration on Ag-ETS-10

Gueibe et al., 2022

- Thermal regeneration durability
  - Regeneration at 170 – 235°C under He
  - Adsorption of 1000 ppm Xe in He
- ➡ **No significant variation on  $q_{Xe}$  &  $t_{10\%}$**
- Radiation resistance
  - External gamma irradiation of 1 MGy
  - "Only" a few hours of operation at MIPFs

➡ **No significant variation on  $q_{Xe}$  &  $t_{10\%}$**

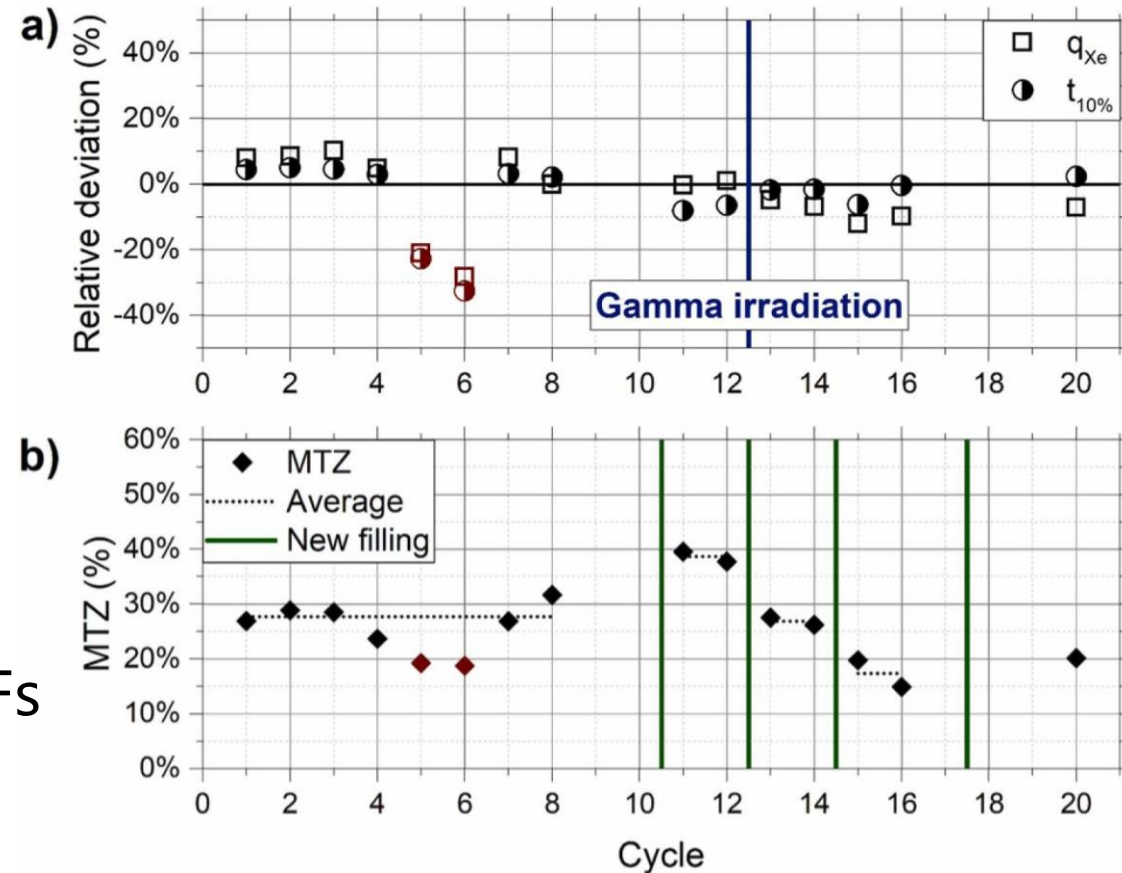

**Variations on Mass Transfer Zone (MTZ) are due to packing**



# New thermal durability investigation



- 44 cycles on Ag-ETS-10
  - Regeneration at  $\pm 210^\circ\text{C}$  (+ test at  $260^\circ\text{C}$ ) under  $\text{N}_2$  (+ test with air)
  - Ads.: 0.087, 10 and 100 ppm Xe in air

➡ **No significant variations on  $q_{\text{Xe}}$  &  $V_{50\%}$**

➡ **Variations on MTZ**

- 43 cycles on Ag-ZSM-5
  - Regeneration at  $\pm 210^\circ\text{C}$  (+ test at  $260^\circ\text{C}$ ) under  $\text{N}_2$  (+ test with air)
  - Ads.: 0.087 and 10 ppm Xe in air

➡ **Variations on  $q_{\text{Xe}}$  &  $V_{50\%}$  likely due to regeneration duration**


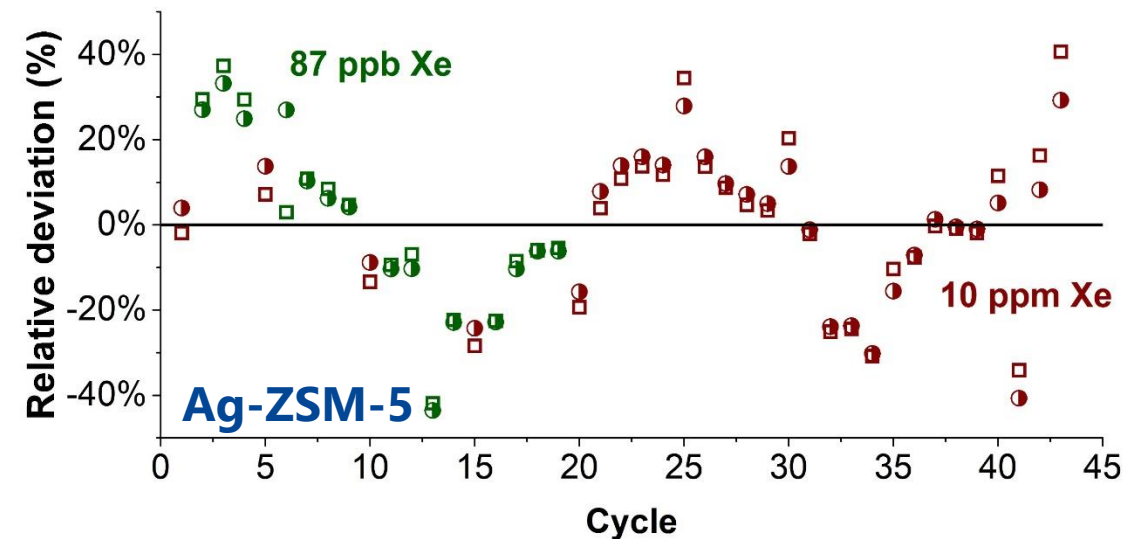
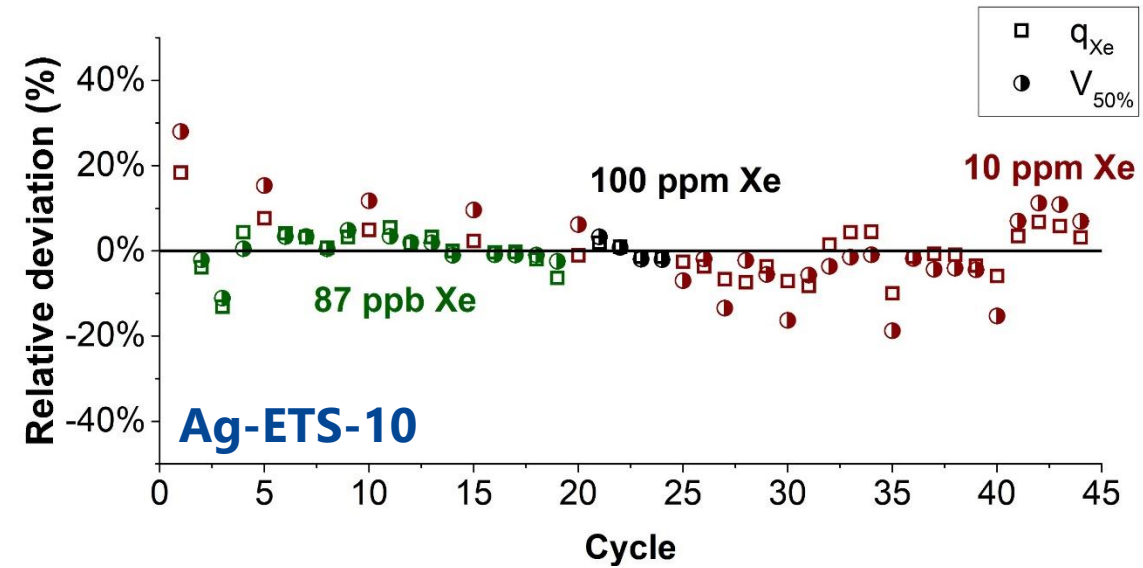




# New in-situ irradiation of AgZs



Adsorption of  $\sim 50$  TBq Xe-133 on  $\sim 30$  g of both AgZs at IRE for 8 days

- Activity distribution estimation with COMSOL Multiphysics® (based on stable Xe experiments)
- Estimation of absorbed dose per 1 cm layer (as sampled after irradiation) by MC
  - Current estimate: 10 – 100 MGy
  - Tens – hundreds of hours of operation
- Characterization of the most irradiated sample
  - Xe adsorption at room temperature
  - SEM/EDX, PXRD,  $^{27}\text{Al}$ - and  $^{29}\text{Si}$  solid-state NMR and microporosity

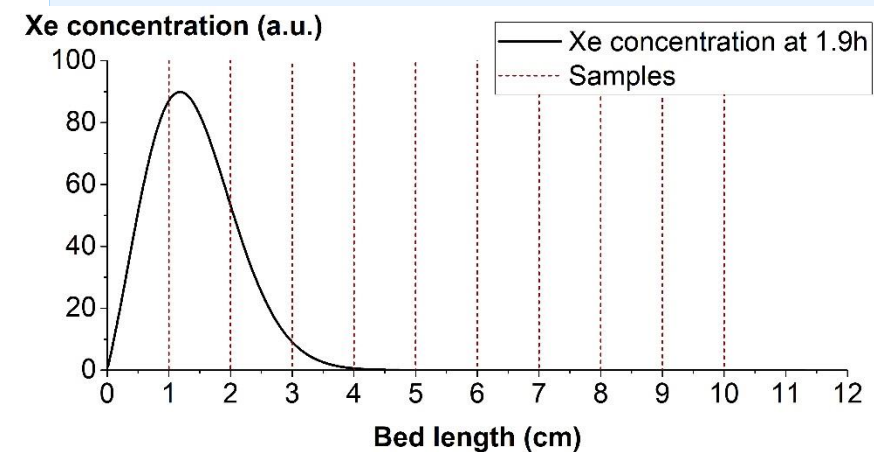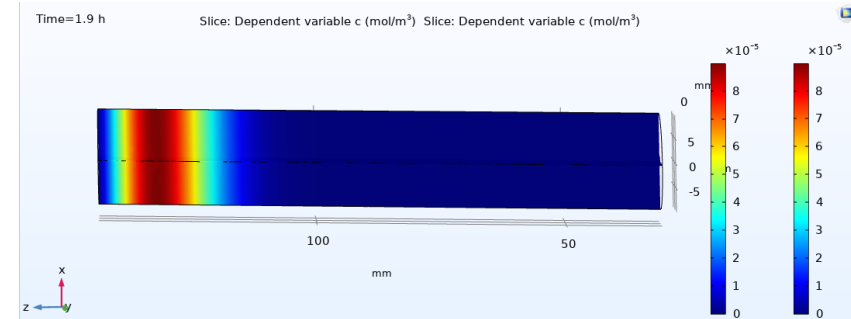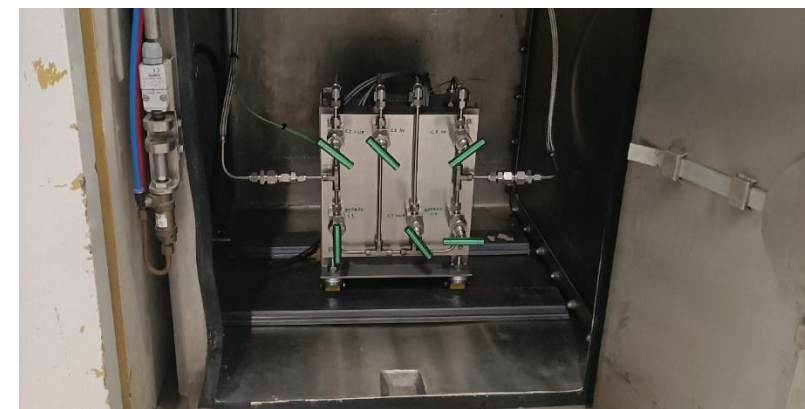

# New in-situ irradiation of AgZs

- No significant degradation on the breakthrough of 10 ppm Xe in nitrogen (packing !)
- No significant differences observed by other characterizations, **EXCEPT**  $^{29}\text{Si}$  NMR on Ag-ETS-10
  - Local changes in the Si environment in Ag-ETS-10

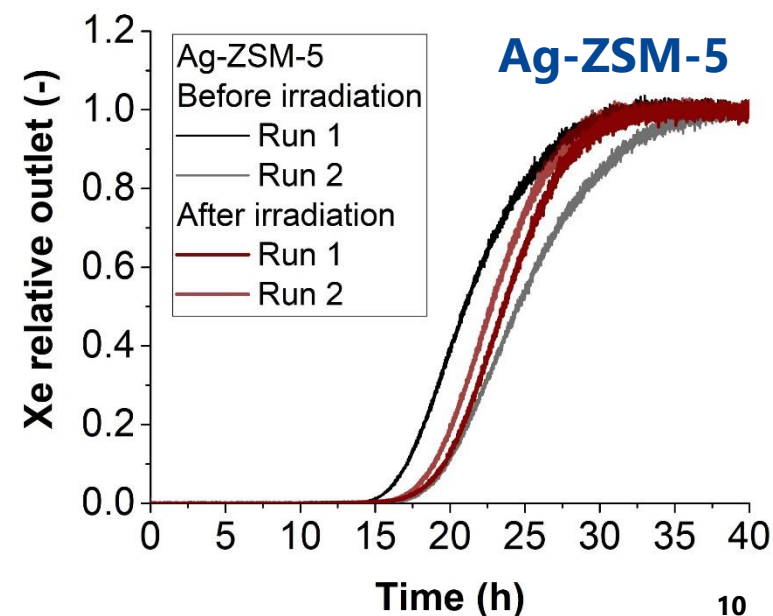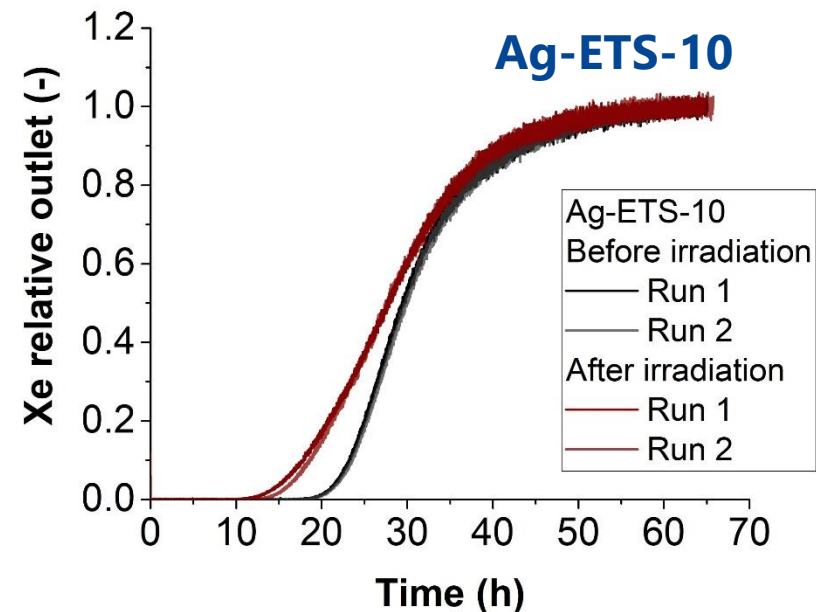


Characterization	Ag-ETS-10		Ag-ZSM-5	
	Thermal cycles	Irradiation	Thermal cycles	Irradiation
SEM/EDX				
PXRD				
$^{27}\text{Al}$ NMR	NA	NA		
$^{29}\text{Si}$ NMR				
Microporosity				

# Conclusions

1. Durability for thermal regeneration
    - No significant degradation observed
    - Packing of Ag-ETS-10 is important on the shape of the breakthrough
    - Variations in Xe adsorption on Ag-ZSM-5 likely from desorption duration
  2. Radiation resistance
    - No significant degradation observed on Ag-ZSM-5
    - No significant degradation observed on Ag-ETS-10, **EXCEPT** on  $^{29}\text{Si}$  NMR
      - Changes in the local environment of Si after irradiation
- Publication is being drafted

# Perspectives

- Future potential work
  - Further characterizations of the irradiated samples (e.g. Ag oxidation states)
  - Further investigation on the  $^{29}\text{Si}$  NMR result on Ag-ETS-10
  - Effect of impurities on the performances of AgZs (e.g. Cl-containing VOCs)
    - This would require a characterization of the gas stream to be treated at facilities
- New adsorbents in general could
  - Simplify mitigation systems (passive, less pre-conditioning needed, ...)
  - Reduce the operation cost (room temperature, smaller systems, ...)
  - Further reduce radionuclide emissions (equivalent but more efficient systems)



**Ideally all three but in practice probably a trade-off between them**



ELSEVIER

Contents lists available at ScienceDirect

## Process Safety and Environmental Protection

journal homepage: [www.elsevier.com/locate/psep](http://www.elsevier.com/locate/psep)



### Application of silver-exchanged zeolite for radioxenon mitigation at fission-based medical isotope production facilities

Christophe Gueibe<sup>a,b,\*</sup>, Jos Rutten<sup>a</sup>, Johan Camps<sup>a,b</sup>, Dominique Moyaux<sup>c</sup>, Wouter Schroeyers<sup>b</sup>, Matthias Auer<sup>d,1</sup>, Sonja Schreurs<sup>b</sup>



ELSEVIER

Contents lists available at ScienceDirect

## Separation and Purification Technology

journal homepage: [www.elsevier.com/locate/seppur](http://www.elsevier.com/locate/seppur)



### Silver-exchanged zeolites for collecting and separating xenon directly from atmospheric air

Christophe Gueibe<sup>a,b,\*</sup>, Jos Rutten<sup>a</sup>, Johan Camps<sup>a,b</sup>, Dominique Moyaux<sup>c</sup>, Wouter Schroeyers<sup>b</sup>, Romano Plenteda<sup>d,1</sup>, Nikolaus Hermanspahn<sup>d</sup>, Daria Minta<sup>e</sup>, Sonja Schreurs<sup>b</sup>



# Thank you for your attention!